

**Nanostructured alumina as seed protectant against three stored-product
insect pests**

**Chiraz Belhamel ^a, Lila Boulekbache–Makhlouf ^a, Stefano Bedini ^{b,*}, Camilla Tani ^b,
Tiziana Lombardi ^b, Paolo Giannotti ^b, Khodir Madani ^{a, c}, Kamel Belhamel ^d, Barbara
Conti ^b**

*^a Laboratoire de Biomathématiques, Biophysique, Biochimie et Scientométrie, Faculté des
Sciences de la Nature et de la Vie, Université de Bejaia, 06000 Bejaia, Algérie.*

*^b Department of Agriculture, Food and Environment, University of Pisa, Via del Borghetto 80,
56124 Pisa, Italy.*

*^c Centre National de Recherche en Technologie Agro-alimentaire, Université de Bejaia,
06000 Bejaia, Algérie.*

*^d Laboratoire des Matériaux Organique, Faculté de Technologie, Université de Bejaia, 06000
Bejaia, Algérie.*

*** Corresponding author: Stefano Bedini, Department of Agriculture, Food and Environment
(DAFE) University of Pisa, No. 80 Via del Borghetto, 56124 Pisa, Italy.**

E-mail: stefano.bedini@unipi.it

Abstract

Nanoparticles represent a promising technology to enhance the efficacy of bioactive materials and a large number of studies showed the effectiveness of nanostructured materials against various arthropod species of economic importance. In this work nanostructured alumina (NSA) was prepared using sol-gel method and the effect of NSA was evaluated as seed protectant against the main seed-infesting insect pests *Oryzaephilus surinamensis* (L.) (Coleoptera: Silvanidae) *Stegobium paniceum* (L.), (Coleoptera: Anobiidae), and *Tribolium confusum* Jacquelin du Val (Coleoptera: Tenebrionidae). Besides, we tested the effects of NSA on seed germination and plant growth and finally, we assessed the presence of NSA as a contaminant in the leaves of bean plants germinated from NSA-treated seeds. The results showed significant insecticidal activity of NSA against the three tested species. After sixteen days, the percentage of insect mortality at the highest NSA concentration tested (400 mg Kg⁻¹) was 100.00% for *S. paniceum* followed by *T. confusum* (79.41%), and *O. surinamensis* (80.64%). Besides, *in-vitro* tests indicated that NSA has no effects on seeds germination and on radicle and shoot elongation. No effects of NSA were also observed in pot tests on the bean's plants. No differences were recorded in the leaves area, stoma density and roots length. On the contrary, the shoot of plants from NSA-treated beans was about 66% higher than the one of the non-treated plants (shoot, 15.07 cm for the control and 22.76 cm for NSA-treated plants). Finally, no contamination by alumina particles was found by EDX-system coupled with Scanning Electron Microscopy (SEM) on the surface of the *P. vulgaris* leaves obtained from NSA-treated beans. Overall, the results showed that NSA could be an effective protective agent for the control insect pests during the seeds storage.

Keywords: *Alumina nanoparticles; Sol-gel; Insecticidal activity; alumina characterization; stored seeds insect pest.*

1. Introduction

Insect pests constitute a major threat not only to stored food and grain (Jayas, 2012) but also to seeds for sowing. Further, due to their high economic value and low acceptable damage threshold, seeds for sowing require particular protection from insect pests resulting in the application of pesticides to overcome yield losses (Pimentel, 2019). These seeds, usually stored in relatively small quantities and in separate packages, are particularly susceptible to insect attack because of their prolonged period of storage, often more than one year (Stejskal, 2015). Moreover, due to the global market, seeds insect infestation promotes the spread of invasive stored food pests (Stejskal et al., 2014).

Currently, the protection of seeds against insect pests relies on mechanical (sieving to remove dust, impurities, and pests before accepting new seed batches into facilities) and on chemical treatments by phosphine, pyrethrins, pyrethroids, neonicotinoids and organophosphates (Stejskal et al., 2015). However, the massive use of synthetic pesticides led to the development of resistance in insect pests, as well as to severe consequences for human health and the environment (Guedes et al., 2006; Ribeiro et al., 2003; Desneux et al., 2007; Daglish et al., 2014; Naqqash et al., 2016).

Neonicotinoids, that are the most widely used class of insecticides worldwide (Longhurst et al., 2013) have been largely used for seed coating, showed to cause a variety of toxic effects to vertebrates including humans (Wang et al., 2018). Moreover, numerous evidences suggest that synthetic insecticides can seriously affect non-target species in natural and agricultural

ecosystems (van der Sluijs et al., 2015) such as pollinators (Tomè et al., 2012; Goulson, 2013), aquatic invertebrates and insectivorous birds (Van Dijk et al., 2013; Hallmann et al., 2014). For these reasons, the use of such chemicals is now under increasing restrictions worldwide (Handford et al., 2015) and new effective, environment-friendly tools for the control of seed-infesting insect pests that avoid the use of synthetic pesticides are strongly needed. In the last years the research has focalized on the use of natural substances such as aromatic plants essential oils and monoterpenes (Tapondjou et al., 2005; Benelli et al., 2015; Bedini et al., 2016; Bedini et al., 2017) and inert dusts (Mewis and Ulrichs, 2001; Lee et al., 2003; Athanassiou et al., 2005; Kljajić et al., 2010; Pierattini et al., 2019). In this regard, nanoparticles technology gave new possibility to manage seeds insect pests avoiding the use of synthetic pesticides (Kumar et al., 2010; Murugan et al., 2015; Athanassiou et al., 2018).

Nanostructured materials have been showed to have properties that are not shared by non-nanoscale particles with the same chemical composition (Auffan et al., 2009). The small size (1-100 nm), results in very large surface/volume ratio per unit weight (Paull and Lyons, 2008), increasing the toxicity of the bioactive substances. Actually, a large number of studies showed the effectiveness of nanoparticles against various arthropod species of economic importance (Athanassiou et al., 2018; Lazarević et al., 2018; Stadler et al., 2009; 2012; 2017; Buteler et al., 2015). Among nanostructured materials, nanostructured alumina (NSA), was showed to be effective as a contact insecticide (Debnath et al., 2011; Kitherian, 2017; Stadler et al., 2017). The present investigation was undertaken with aim to assess the potential of NSA synthesized by sol-gel method as crop-plant seeds protecting against seed-infesting insect pests.

For this purpose, we evaluated the effect of NSA-treated seeds on the main seed-infesting insect pests *Oryzaephilus surinamensis* (L.) (Coleoptera: Silvanidae) (Michael & Zimmerman 1990; David et al. 2013) *Stegobium paniceum* (L.), (Coleoptera: Anobiidae) (Doijode, 2012), and *Tribolium confusum* Jacquelin du Val (Coleoptera: Tenebrionidae) (Hagstrum &

Subremanyam, 2016). Besides, we tested the effects of NSA on seed germination and plant growth and, finally, we assessed the presence of NSA as a contaminant in the leaves of plants germinated from NSA-treated seeds.

2. Materials and methods

2.1. NSA preparation and characterization

NSA was prepared by the method described by Li et al. (2006) with little modifications. A preliminary solution was prepared by sol-gel method as follows: 0.5 M aluminium nitrate and 50 mL 1, 4-butandiol were gradually added to 200 mL 1:1 water-ethanol solution. Then, the solution was placed on a hot plate at 40 °C for 30 min. 0.55 mL Citric acid (0.55 mL) was dissolved in 40 mL deionized water, were added to the solution and continuously stirred until a colloidal solution was prepared. The obtained solution was heated in a water bath at 80 °C for 18 h to evaporate the solvent and then placed on a hot plate at 120 °C for 4 h until the viscosity and colour changed as the solution turned into a transparent stick gel. The obtained sol-gel precursors were then dried at 200 °C for 12 h in an oven and grinded into powders. Finally, the pale brown powder obtained after gel drying, was heated at 1000 °C for 1 h. The NSA obtained were characterized by X-ray diffraction (XRD) and Fourier Transform Infrared Spectroscopy (FT-IR spectroscopy) analyses. The XRD analysis is one of the most widely used, empirical evidence to estimate the crystalline size of nanoparticles (Guczi et al., 2003; Lemine, 2009; Pradeep et al., 2008; Sheng et al. 1998). The structure of NSA particles was investigated using a X'Pert Analytical type MPD multi-purpose X-ray diffraction system piloted by the X'Pert Hi Score software (Malvern Panalytical Ltd, Malvern, UK) to display, treat, index, and match the diffraction data to known phases (Degen et al., 2014).

FT-IR spectroscopy analysis of NSA was carried out using a IRAffinity-1 CE infrared spectrophotometer (Shimadzu, Kyoto, Japan) over the range of 4000 to 400 cm⁻¹. The analysis was carrying out at room temperature on KBr discs made up of 10 mg of NSA samples mixed in about 150 mg of ground KBr (IR grade, > 99%). The powder was pressed into pellets (Ø = 10 mm) with low pressure (~1.5 psi) (Dablemont et al., 2008).

2.2. Insect rearing

Oryzaephilus surinamensis, *S. paniceum*, and *T. confusum* were reared at room temperature, 65% relative humidity (RH), natural photoperiod, in PVC boxes (20 × 25 × 15 cm) containing a mixture of chickpeas, beans, maize, and wheat grains and covered by a nylon net allowing air exchange. Adults (about 7 days old) were used for the bioassays (Bougherra et al., 2015).

2.3. Insecticidal activity of NSA

The insecticidal efficacy was tested mixing the NSA with the beans at the doses of 0 (control), 25, 50, 100, 200, and 400 mg Kg⁻¹ of seeds. *Phaseolus vulgaris* L. var. “Piattelli” seeds were shaken manually for 10 minutes with each dose of NSA in a glass jar (750 mL) to achieve an even distribution in the entire seeds mass. Then, 10 unsexed adults of each insect species were added into each jar. The jars were placed in an incubator at 27 ± 1°C, 60% RH and in the darkness. The insects were considered dead when no leg or antenna movements were observed after prodding them with a fine brush. Depending on the number of specimens available, five (*O. surinamensis* and *T. confusum*) or three (*S. paniceum*) replicates for each NSA dose were performed (78 experimental units, in total). The mortality percentage was then determined after

3, 6, 9, 12, and 16 days and adjusted by the Abbott's formula on the basis of the controls' mortality.

2.4. Effects of NSA on *P. vulgaris*

2.4.1. *In vitro* tests

Seeds of *P. vulgaris* var. "Piattelli" uniform in size were checked for their viability by suspending them in deionized water. The seeds were then surface sterilized in a 10% sodium hypochlorite solution for 10 minutes and rinsed through with deionized water several times. The NSA were dispersed in deionized water by ultrasonic vibration to obtain a concentration of 1.6 mg mL^{-1} and maintained in suspension by magnetic stirrer until use. A disc of Whatmann No. 1 filter paper was placed into a Petri dish ($10 \times 15 \text{ mm}$) and 10 mL of the NSA suspension were added. Ten seeds were then transferred onto the filter paper and the Petri dish covered and sealed with tape. The Petri dish was then placed in an incubator for 5 days at $25 \pm 1^\circ\text{C}$ in darkness. Control seeds were treated with 5 ml of deionized water only. The germination of the seeds was checked daily and the Germination Percentage (GP) was calculated according to Lombardi et al. (2019) by the following formula:

$$\text{GP} = (\text{germinated seeds} / \text{total seeds tested}) \times 100.$$

P. vulgaris seedlings' root and hypocotyl elongation was measured at the end of the trial. Five replications for treatment were performed.

2.4.2. *In pot* tests

The effects of NSA on plant growth were investigated by pot culture. A 1.6 mg mL⁻¹ NSA solution was prepared as above reported. 150 mL (240 mg NSA) of the suspension were used to wet a sterilized filter paper disk (10 cm Ø). Seeds of *P. vulgaris* var. “Piattelli” were immersed in a 10% sodium hypochlorite solution for 10 min to ensure surface sterility, rinsed in deionised water and each seed was then wrapped in a sterilized filter paper charged with the NSA solution. The wrapped seeds were then sown in pots containing 800 ml of substrate (Universal Toprak Virgoplant, Leroymerlin, Livorno, Italy). Three seeds were sown in each pot. As control, the seeds were wrapped in sterilized filter paper wetted by deionized water only. Three replicates for each NSA treatment and the control (0 mg Kg⁻¹) were performed. The beans seedlings were grown for 7 days in a grow chamber at 25°C (day) and 23°C (night), with a 16:8 h light: dark photoperiod (photosynthetically active radiation intensity 280 µE s⁻¹ m⁻²) and 60 ± 10% relative humidity. After 14 days root and shoot elongation were measured.

2.4.3. SEM-EDX microanalysis

SEM-EDX microanalysis were performed on NSA to confirm their composition and on the leaves of the plants obtained from seeds treated with NSA to assess the contamination of the plants by NSA. For the NSA microanalysis a little amount of the powder was adhered to an aluminium stub using carbon tape glued on both sides and were directly put on the stage of the electron microscopy chamber. Five lectures of the elemental composition were performed on five different particles of the sample. As for the plant, five leaf samples (1 cm²) were cut from fresh leaves of *P. vulgaris* var. “Piattelli” obtained from seeds treated or not treated with 240 mg NSA and grown as reported above. The samples were individually attached to aluminium stubs using a carbon tape glued on both sides and were directly put on the stage of an environmental scanning electron microscopy (ESEM) (FEI Quanta 200, Netherlands) and

194 analysed. The elemental analysis was obtained by an energy-dispersive X- ray analysis (EDX)
195 system performed in the ESEM chamber using a Bruker X-Flash 6/30 Detector. The chamber
196 pressure and accelerating voltage were 130 Pa and 10 kV, respectively.

198 2.5. Data analysis

199
200 The correlation between the mortality of the insect pest species and the NSA dose was
201 determined by univariate linear regression analysis. The insecticidal effect of NSA among the
202 species were investigated by a mixed model two-way analysis of variance with repeated
203 measures (RM-ANOVA). The RM-ANOVA model included the species as between-subjects
204 factor and the time of exposition as within-subjects variable with their interaction. The NSA
205 dose was considered as covariate and its effect was controlled in the analysis. Greenhouse-
206 Geisser correction was applied in case of violation of Mauchly's test of sphericity ($P < 0.05$).
207 The estimated marginal (EM) means of the insect pests' mortality are reported. Comparisons
208 between EM means were performed by pairwise comparison adjusted by Bonferroni correction
209 for multiple comparisons. Differences between plant germination, and plant growth data of
210 NSA-treated and NSA-non-treated samples were analysed by two-tailed student's t-test.
211 Percentage data (insect mortality and seeds germination) were arcsine transformed prior to
212 statistical analysis. All analyses were performed by SPSS 22.0 software (IBM SPSS Statistics,
213 Armonk, North Castle, New York, USA).

215 3. Results

217 3.1. Alumina gel characterization

XRD alumina-gel analysis showed wide peaks corresponding to NSA (Figure 1). The average crystallite size of alumina powder obtained was 56.9 nm. Broad peaks at 37°, 43°, and 66° 2 θ in the XRD spectrum indicated a conversion to slightly amorphous alumina (Table 1). All the detectable peaks can be attributed to the NSA.

The results of the FT-IR analysis are shown (Figure 2). The broad smooth absorption from 550 to 900 cm⁻¹ reveals the formation of NSA. Significant spectroscopic strips at 1381, 1559, 1655, 1681 and 1736 cm⁻¹ were identified as the absorption bands characteristic of H₂O and CO₂. Peaks localized at 3400 and 3500 cm⁻¹ were assigned to stretching vibration and deformation vibration of liaison O-H.

3.2. Insecticidal effect of NSA

The toxicity assay of NSA showed a strong dose-effect relationship between NSA doses and insect mortality (*O. surinamensis*: $R = 0.684$; $F_{1,13} = 11.426$; $P = 0.005$; *S. paniceum*: $R = 0.952$; $F_{1,10} = 95.909$; $P \leq 0.001$; *T. confusum*: $R = 0.758$; $F_{1,13} = 17.535$; $P = 0.001$) (Figure 3A, 3B, 3C). After sixteen days, the percentage of insect mortality at the highest NSA concentration tested (400 mg Kg⁻¹) was 100.00% for *S. paniceum* followed by *T. confusum* (79.41%), and *O. surinamensis* (80.64%). Repeated measures ANOVA showed a significant within-subjects effects of the time of exposition on mortality of the three specie after controlling for the effects of the NSA dose ($F_{3, 152} = 94.233$; $P < 0.001$; $\eta_p^2 = 0.623$) with a significant interaction of the time x dose ($F_{3, 152} = 14.991$; $P < 0.001$; $\eta_p^2 = 0.208$) and of the time x species ($F_{3, 152} = 6.587$; $P < 0.001$; $\eta_p^2 = 0.188$). The effect of the species (between-subject effect) was significant also ($F_{2, 57} = 12.689$; $P < 0.001$; $\eta_p^2 = 0.308$). The estimated marginal means (evaluated at NSA = 151.23 mg kg⁻¹) showed that the most susceptible species was *S. paniceum* (mean = 36.08%) followed by *T. confusum*, and *O. surinamensis* (mean = 28.55, and 23.04, respectively) (Table

2). Pairwise comparisons of EM means showed that *S. paniceum* was significantly more susceptible to NSA than the other two insect species (Table 2). Median lethal concentration (LC₅₀) values calculated by Probit analysis were 61.53, 14.87, and 127.17 mg Kg⁻¹ for *O. surinamensis*, *S. paniceum*, and *T. confusum*, respectively (Table 3). Consistently with the RM-ANOVA, RMP analysis showed that, *S. paniceum* was significantly more susceptible to NSA than *O. surinamensis* (*S. paniceum* vs *O. surinamensis* RMP = 0.242; 95% CI: 0.034; 0.770) and *T. confusum* (*S. paniceum* vs *T. confusum* RMP = 0.117; 95% CI: 0.010; 0.403).

3.3. Effects of NSA on *P. vulgaris*

The NSA treatment of the beans did not affect the *P. vulgaris* germination ($t_8 = 1.159$, $P = 0.192$) nor the seedlings' root and hypocotyl elongation ($t_8 = 1.074$, $P = 0.341$; $t_8 = 1.159$, $P = 0.280$, respectively) (Table 4).

No negative effect on the beans plants was observed also in pot culture. After 14 days from the seedlings emergence no differences were recorded for the leaves area, stoma density, and root length ($t_4 = 2.008$; $P = 0.115$; $t_4 = 2.456$; $P = 0.070$; $t_4 = 0.640$; $P = 0.557$, respectively). On the contrary, we observed a positive effect of the NSA on the shoot growth ($t_4 = 2.974$; $P = 0.041$) with the treated plants that were about 66% higher than the non-treated plants (Table 5).

3.4. SEM-EDX microanalysis

The chemical analyses of the particles showed that the main element was aluminium ($51.0 \pm 0.1\%$) followed by oxygen ($46.6\% \pm 1.2$) and carbon ($2.2 \pm 0.3\%$).

The possible contamination of *P. vulgaris* plants by the NSA used for the seeds treatments was checked by SEM-EDX. The analysis carried out on the bean leaves revealed the presence

of elements constituents of the plant's tissues (oxygen, 66.6 ± 1.4 ; carbon, 33.2 ± 2.3 ; potassium, $0.2 \pm 0.1\%$) while no evidence of NSA was found.

4. Discussion

The results of the X-ray diffraction (XRD) analysis consisting in well-resolved peaks, confirmed the polycrystalline and monophasic nature of the prepared material. The diffraction peaks provided a clear evidence of the formation of NSA with an average particle size of 56 nm. The elemental analysis of nanostructured alumina by energy-dispersive X-ray analysis (EDX) of nanostructured alumina confirms the presence of Al, O and C with mass percentage 34.83%, 33.97% and 31.19%, respectively. Rogojan et al. (2009) demonstrate that crystallite sizes obtain from X-ray diffraction images for the alumina powders using sol-gel methods is 10.70 nm. The differences between two results can probably explained by measuring the angles and intensity of the diffracted rays, the symmetries of the crystal structure (space group) and a three-dimensional image of the electron density in the lattice. From this density, the average position of the atoms of the crystal forming the crystal pattern can be determined as well as the nature of these atoms, their chemical bonds, their thermal agitation.

The result of FTIR allowed to clarify the structure-spectral relationships of the associated molecular vibrations, the resulting peak bands at 550 to 900 cm^{-1} can be attributed to the formation of alumina-oxygen. Janbey et al. (2001) reported that IR spectra shows the strong absorption bands at 1600 cm^{-1} due to the various vibration made of triethanolamine the metal ions also the bands appearing at 1005 and 800 cm^{-1} could be attributed to the presence of nitrates ions and bands appeared in the region 700-400 cm^{-1} could be the results of some trace amounts of metal oxides.

The toxicity bioassay showed the NSA is able to exert a significant insecticidal activity against the main seeds pests *O. surinamensis*, *S. paniceum*, and *T. confusum*.

According to our results, the most susceptible species to the NSA was *S. paniceum*, while *O. surinamensis* resulted the most resistant one.

Although no previous studies are available on the effects of NSA on the species tested in this work, in line with our results Stadler et al. (2009) reported 100% mortality of the stored grain pests *Rhyzoperta dominica* (Coleoptera: Bostrichidae) and *Sitophilus oryzae* (Coleoptera: Curculionidae) adults in wheat treated with 1000 mg kg⁻¹ of NSA dust after 9 days of exposure and about 95% mortality after only 3 days of exposure. A high effectiveness of NSA was observed also by Goswami et al. (2010) with about 90% of mortality of *S. oryzae* and *Tribolium castaneum* (Coleoptera: Tenebrionidae) exposed for 7 days to 2000 mg kg⁻¹ of hydrophilic NSA. Similarly, NSA produced by combustion of glycine and aluminium nitrate caused more than 94% mortality of *S. oryzae* adults after 15 days of exposure applied on wheat at doses ranging from 62.5 to 1000 mg kg⁻¹ (Stadler et al., 2012). Nevertheless, the efficacy of this NSA for control of *R. dominica* adults resulted in lower overall mortality levels than for *S. oryzae*. Similar results were obtained when three novel NSA dusts, based on chemical solution methods, were applied on wheat for control of *R. dominica* and *S. oryzae* (Buteler et al., 2015) and Stadler et al. (2017) obtained a LC₅₀ of 79.91 mg Kg⁻¹ after 39 days of exposition with a LT₅₀ of 23.82 days when tested at 500 mg kg⁻¹ for NSA against *S. oryzae*.

The insecticidal effect of the NSA could be probably due to the electrically charged particles resulting by the oxidation of aluminium. Alumina electrically charged particles, showing interaction between dipole-dipole promote the formation of aggregates that stick firmly to the insect cuticle wax layer and generated electric charges resulting by triboelectric effect (Pimentel, 2005). In addition, according to Stadler et al. (2012) and Buteler et al. (2015) the toxic effect of the NSA, similarly to those of other insecticidal dust such as diatomaceous

earth should be due to the absorption by NSA of the epicuticular lipids, causing the insect death by dehydration. The insecticidal effect should also depend on NSA physical characteristics, (i.e. particle size, particle morphology) and on other biotic and abiotic factors such as target species, and relative humidity (Stadler et al., 2012; Buteler et al., 2015).

We observed no significant effect of NSA on plant germination, seedlings elongation and plant growth, nor we observed any aluminate contamination on the surface of the *P. vulgaris* leaves.

Nanoparticles can penetrate into the plant through the stomatal openings or the bases of trichomes and then transferred to various tissue (Fernández and Eichert, 2009). Previous studies showed that nanoparticles whose diameter is less than the pore diameter can reach the plasmatic membrane and cross it with incorporated transport carrier proteins or through ionic channels interfering with metabolic processes (Jia et al., 2005) and reaching mitochondria or nucleoli in both plant and insect tissues (Yasur and Rani 2013, 2015). For this reason, it is important to assess the phytotoxicity of nanomaterials. Lee et al. (2010) evaluated the effect of four metal oxide nanoparticles, aluminium oxide ($n\text{Al}_2\text{O}_3$), silicon dioxide ($n\text{SiO}_2$), magnetite ($n\text{Fe}_3\text{O}_4$), and zinc oxide ($n\text{ZnO}$), on the development of *Arabidopsis thaliana* (L.) Heynh (Brassicaceae) (seed germination, root elongation, and number of leaves) and, in accordance with our results, found that aluminium oxide nanoparticles were no toxic whereas they observed a toxic effect of the other three metal oxide nanoparticles. The absence of effect of aluminium oxide nanoparticles on seed germination and root growth was also observed by Lin and Xing (2007) who showed that the nanoparticles have no adverse effects on California red beans, while Mahajan et al. (2011) observed a positive effect on seedlings growth of *Vigna radiata* (L.) Wilczek, and *Cicer arietinum* L. (Fabaceae) after a treatment by ZnO nanoparticles.

In this experiment, the only effects of the NSA we observe is the increase of shoot growth in the treated plants that were about 66% higher than the non-treated ones (length of the shoot 15.07 ± 1.20 cm for the control and 22.76 ± 2.25 cm for NSA treatment). In line with our results, Khodakovskaya et al. (2009) observed that nanostructured carbon determines an increase on tomato plants seed germination and the plant growth and, according to the authors, such a positive effect of the nanoparticles could be due to their ability to penetrate the seed coat and enhance the water uptake.

Nanotechnology has a huge potential to develop alternative pest control strategy. In this study, we showed that alumina nanoparticles synthesized by sol-gel method could be an effective protective agent that can be used to control the infestations of insect pests during the seeds storage. Recently, the international community has paid great attention to issues of environmental sustainability. In particular, the target 3.9 of the ONU 2030 Agenda for Sustainable Development is aimed to substantially reduce, by 2030 the number of deaths and illnesses from hazardous chemicals and air, water and soil pollution and contamination. Even if further studies are needed to evaluate the efficacy of NSA seed treatments under a wide range of applicative conditions our results showing the efficacy of NSA against the insect pest species and the absence of negative effects on the seeds germination and plant growth indicate that NSA may be a valid alternative to the chemical synthetic insecticides currently used for seeds coating.

Acknowledgments

The authors thank the Ministry of High Education and Scientific Research of Algeria for their financial support. This work was also supported by Italian Ministero dell'Istruzione, dell'Università e della Ricerca (MIUR), BIOPIC, 2015BABFCF.

366

367 **References**

368

369 Athanassiou, C. G., Kavallieratos, N. G., Benelli, G., Losic, D., Rani, P. U., & Desneux, N.
370 (2018). Nanoparticles for pest control: current status and future perspectives. *Journal of*
371 *pest science*, 91(1), 1-15.

372 Athanassiou, C. G., Vayias, B. J., Dimizas, C. B., Kavallieratos, N. G., Papagregoriou, A. S.,
373 & Buchelos, C. T. (2005). Insecticidal efficacy of diatomaceous earth against *Sitophilus*
374 *oryzae* (L.)(Coleoptera: Curculionidae) and *Tribolium confusum* du Val (Coleoptera:
375 Tenebrionidae) on stored wheat: influence of dose rate, temperature and exposure interval.
376 *Journal of Stored Products Research*, 41(1), 47-55.

377 Auffan, M., Rose, J., Bottero, J. Y., Lowry, G. V., Jolivet, J. P., & Wiesner, M. R. (2009).
378 Towards a definition of inorganic nanoparticles from an environmental, health and safety
379 perspective. *Nature nanotechnology*, 4(10), 634.

380 Bedini, S., Bougherra, H. H., Flamini, G., Cosci, F., Belhamel, K., Ascrizzi, R., & Conti, B.
381 (2016). Repellency of anethole-and estragole-type fennel essential oils against stored grain
382 pests: the different twins. *Bullettin of Insectology*, 69(1), 149-57.

383 Bedini, S., Flamini, G., Cosci, F., Ascrizzi, R., Echeverria, M. C., Guidi, L., Landi, M., Lucchi,
384 A., & Conti, B. (2017). *Artemisia* spp. essential oils against the disease-carrying blowfly
385 *Calliphora vomitoria*. *Parasites & vectors*, 10(1), 80.

386 Benelli, G., Bedini, S., Flamini, G., Cosci, F., Cioni, P. L., Amira, S., Benchikh, F., Laouer, H.,
387 Di Giuseppe, & Conti, B. (2015). Mediterranean essential oils as effective weapons against
388 the West Nile vector *Culex pipiens* and the *Echinostoma* intermediate host *Physella acuta*:
389 what happens around? An acute toxicity survey on non-target mayflies. *Parasitology*
390 *research*, 114(3), 1011-1021.

391 Bougherra, H. H., Bedini, S., Flamini, G., Cosci, F., Belhamel, K., & Conti, B. (2015). *Pistacia*
392 *lentiscus* essential oil has repellent effect against three major insect pests of pasta.
393 *Industrial Crops and Products*, 63, 249-255.

394 Buteler, M., Sofie, S. W., Weaver, D. K., Driscoll, D., Muretta, J., & Stadler, T. (2015).
395 Development of nanoalumina dust as insecticide against *Sitophilus oryzae* and
396 *Rhyzopertha dominica*. *International journal of pest management*, 61(1), 80-89.

397 Dablemont, C., Lang, P., Mangeney, C., Piquemal, J. Y., Petkov, V., Herbst, F., & Viau, G.
398 (2008). FTIR and XPS study of Pt nanoparticle functionalization and interaction with
399 alumina. *Langmuir*, 24(11), 5832-5841.

400 Daglish, G. J., Nayak, M. K., & Pavic, H. (2014). Phosphine resistance in *Sitophilus oryzae* (L.)
401 from eastern Australia: Inheritance, fitness and prevalence. *Journal of Stored Products*
402 *Research*, 59, 237-244.

403 Debnath, N., Das, S., Seth, D., Chandra, R., Bhattacharya, S. C., &
404 Goswami, A. (2011). Entomotoxic effect of silica nanoparticles against *Sitophilus oryzae*
405 (L.). *Journal of Pest Science*, 84(1), 99-105.

406 Degen, T., Sadki, M., Bron, E., König, U., & Nénert, G. (2014). The highscore suite. *Powder*
407 *Diffraction*, 29(S2), S13-S18.

408 Desneux, N., Decourtye, A., & Delpuech, J. M. (2007). The sublethal effects of pesticides on
409 beneficial arthropods. *Annual Review of Entomology*, 52, 81-106.

410 Doijode D.S. (2012) Seed Storage of Horticultural Crops. Ed. CRC, 339 pp.

411 Fernández, V., & Eichert, T. (2009). Uptake of hydrophilic solutes through plant leaves: current
412 state of knowledge and perspectives of foliar fertilization. *Critical Reviews in Plant*
413 *Sciences*, 28(1-2), 36-68.

414 Goswami, A., Roy, I., Sengupta, S., & Debnath, N. (2010). Novel applications of solid and
415 liquid formulations of nanoparticles against insect pests and pathogens. *Thin solid films*,
519(3), 1252-1257.

416 Goulson, D. (2013). An overview of the environmental risks posed by neonicotinoid
 417 insecticides. *Journal of Applied Ecology*, 50(4), 977-987.

418 Gucci, L., Beck, A., Horváth, A., Koppány, Z.S., Stefler, G., Frey, K., Sajó, I., Geszti, O., Bazin,
 419 D. & Lynch J., (2003). AuPd bimetallic nanoparticles on TiO₂: XRD, TEM, in situ EXAFS
 420 studies and catalytic activity in CO oxidation. *Journal of Molecular Catalysis A: Chemical*,
 421 204-205, 545-552.

422 Guedes, R. N. C., Oliveira, E. E., Guedes, N. M. P., Ribeiro, B., & Serrão, J. E. (2006). Cost
 423 and mitigation of insecticide resistance in the maize weevil, *Sitophilus zeamais*.
 424 *Physiological Entomology*, 31(1), 30-38.

425 Hagstrum D & Subremanyam B. (2016) Stored Products Insect Resource. Elsevier 518 pp.

426 Hagstrum, D.W., Klejdysz, T., Subramanyam, B., Nawrot J. (2013) Atlas of Stored-product
 427 Insects and Mites. Ed Elsevier, 589 pp.

428 Hallmann, C. A., Foppen, R. P., van Turnhout, C. A., de Kroon, H., & Jongejans, E. (2014).
 429 Declines in insectivorous birds are associated with high neonicotinoid concentrations.
 430 *Nature*, 511(7509), 341-343.

431 Handford, C. E., Elliott, C. T., & Campbell, K. (2015). A review of the global pesticide
 432 legislation and the scale of challenge in reaching the global harmonization of food safety
 433 standards. *Integrated environmental assessment and management*, 11(4), 525-536.

434 Janbey, A., Pati, R. K., Tahir, S., & Pramanik, P. (2001). A new chemical route for the synthesis
 435 of nano-crystalline α -Al₂O₃ powder. *Journal of the European Ceramic Society*, 21(12),
 436 2285-2289.

437 Jayas, D. S. (2012). Storing grains for food security and sustainability. *Agricultural Research*,
 438 1(1), 21-24.

439 Jia, G., Wang, H., Yan, L., Wang, X., Pei, R., Yan, T., Zao, Y., & Guo, X. (2005). Cytotoxicity
 440 of carbon nanomaterials: single-wall nanotube, multi-wall nanotube, and fullerene.
 441 *Environmental science & technology*, 39(5), 1378-1383.

442 Khodakovskaya, M., Dervishi, E., Mahmood, M., Xu, Y., Li, Z., Watanabe, F., & Biris, A. S.
 443 (2009). Carbon nanotubes are able to penetrate plant seed coat and dramatically affect seed
 444 germination and plant growth. *ACS nano*, 3(10), 3221-3227.

445 Kitherian, S. (2017). Nano and bio-nanoparticles for insect control. *Research Journal of*
 446 *Nanoscience and Nanotechnology*, 7, 1-9.

447 Kljajić, P., Andrić, G., Adamović, M., & Golić, M. P. (2010). Laboratory evaluation of
 448 insecticidal effectiveness of a natural zeolite formulation against *Sitophilus oryzae* (L.),
 449 *Rhyzopertha dominica* (F.) and *Tribolium castaneum* (Herbst) in treated wheat. *Julius-*
 450 *Kühn-Archiv*, (425), 863.

451 Kljajić, P., Andrić, G., Adamović, M., Bodroža-Solarov, M., Marković, M., & Perić, I. (2010).
 452 Laboratory assessment of insecticidal effectiveness of natural zeolite and diatomaceous
 453 earth formulations against three stored-product beetle pests. *Journal of Stored Products*
 454 *Research*, 46(1), 1-6.

455 Kumar, S., Upadhyaya, J. S., & Negi, Y. S. (2010). Preparation of nanoparticles from corn cobs
 456 by chemical treatment methods. *BioResources*, 5(2), 1292-1300.

457 Lazarević, J., Radojković, A., Kostić, I., Krnjajić, S., Mitrović, J., Kostić, M. B. & Branković,
 458 G. (2018). Insecticidal impact of alumina powders against *Acanthoscelides obtectus*
 459 (Say). *Journal of Stored Products Research*, 77, 45-54.

460 Lee, C.W., Mahendra, S., Zodrow, K., Li, D., Tsai, Y.C., Braam, J. & Alvarez, P.J. (2010)
 461 Developmental phytotoxicity of metal oxide nanoparticles to *Arabidopsis thaliana*.
 462 *Environmental Toxicology and Chemistry*, 29, 669-675.

463 Li, J., Pan, Y., Xiang, C., Ge, Q., & Guo, J. (2006). Low temperature synthesis of ultrafine α -
 464 Al_2O_3 powder by a simple aqueous sol-gel process. *Ceramics International*, 32(5), 587-
 465 591.

466 Lin, D., & Xing, B. (2007). Phytotoxicity of nanoparticles: inhibition of seed germination and
 467 root growth. *Environmental pollution*, 150(2), 243-250.

468 Lombardi, T., Bedini, S., & Bertacchi, A. (2019). Germination ecology of the aromatic
 469 halophyte *Artemisia caerulescens* L.: influence of abiotic factors and seed after-ripening
 470 time. *Folia Geobotanica*, 54(1-2), 115-124.

471 Longhurst, C., Babcock, J. M., Denholm, I., Gorman, K., Thomas, J. D., & Sparks, T. C. (2013).
 472 Cross-resistance relationships of the sulfoximine insecticide sulfoxaflor with
 473 neonicotinoids and other insecticides in the whiteflies *Bemisia tabaci* and *Trialeurodes*
 474 *vaporariorum*. *Pest management science*, 69(7), 809-813.

475 Mahajan, P., Dhoke, S. K., & Khanna, A. S. (2011). Effect of nano-ZnO particle suspension on
 476 growth of mung (*Vigna radiata*) and gram (*Cicer arietinum*) seedlings using plant agar
 477 method. *Journal of Nanotechnology*, 2011.

478 Michael, L. & Zimmerman, A., (1990) Coleoptera Found in Imported Stored-Food Products
 479 Entering Southern California and Arizona between December 1984 through December
 480 1987 The Coleopterists Bulletin Vol. 44, No. 2 (Jun., 1990), pp. 235-240 (6 pages) Ed. The
 481 Coleopterists Society.

482 Murugan, K., Benelli, G., Ayyappan, S., Dinesh, D., Panneerselvam, C., Nicoletti, M., Hwang,
 483 J.S., Kumar, P.M., Subramaniam, J., & Suresh, U. (2015). Toxicity of seaweed-synthesized
 484 silver nanoparticles against the filariasis vector *Culex quinquefasciatus* and its impact on
 485 predation efficiency of the cyclopoid crustacean *Mesocyclops longisetus*. *Parasitology*
 486 *research*, 114(6), 2243-2253.

487 Naqqash, M. N., Gökçe, A., Bakhsh, A., & Salim, M. (2016). Insecticide resistance and its
 488 molecular basis in urban insect pests. *Parasitology research*, 115(4), 1363-1373.

489 Paull, J., & Lyons, K. (2008). Nanotechnology: the next challenge for organics. *Journal of*
 490 *Organic Systems*, 3(1), 3-22.

491 Pierattini, E. C., Bedini, S., Venturi, F., Ascrizzi, R., Flamini, G., Bocchino, R., Girardi, J.,
 492 Giannotti, P., Ferroni, G., & Conti, B. (2019). Sensory quality of essential oils and their
 493 synergistic effect with diatomaceous earth, for the control of stored grain insects. *Insects*,
 494 10(4), 114.

495 Pradeep, A., Priyadharsini, P. & Chandrasekaran, G. (2008). Sol-gel route of synthesis of
 496 nanoparticles of MgFe_2O_4 and XRD, FTIR and VSM study. *Journal of Magnetism and*
 497 *Magnetic Materials*, 320(21), 2774-2779.

498 Pimentel, D. (2019). World Food, Pest Losses, and the Environment. CRC Press.

499 Pimentel, D., & Burgess, M. (2014). Environmental and economic costs of the application of
 500 pesticides primarily in the United States. In *Integrated pest management* (pp. 47-71).
 501 Springer, Dordrecht.

502 Pimentel, D., Hepperly, P., Hanson, J., Douds, D., & Seidel, R. (2005). Environmental,
 503 energetic, and economic comparisons of organic and conventional farming systems.
 504 *BioScience*, 55(7), 573-582.

505 Ribeiro, B. M., Guedes, R. N. C., Oliveira, E. E., & Santos, J. P. (2003). Insecticide resistance
 506 and synergism in Brazilian populations of *Sitophilus zeamais* (Coleoptera: Curculionidae).
 507 *Journal of Stored Products Research*, 39(1), 21-31.

508 Rogojan, R., Andronescu, E., Ghitulica, C., & Vasile, B. S. (2011). Synthesis and
 509 characterization of alumina nano-powder obtained by sol-gel method. *UPB Buletin*
 510 *Stiintific, Series B: Chemistry and Materials Science*, 73(2), 67-76.

511 Sheng, H. W., Lu, K. & Ma, E. (1998). Melting of embedded Pb nanoparticles monitored
 512 using high-temperature *in situ* XRD. *Nanostructured Materials*, 10(5), 865-873

513 Stadler T, Buteler M, Weaver D (2009) Novel use of nanostructured alumina as an
 514 insecticide. *Pest management science*, 66, 577-579.

515 Stadler, T., Buteler, M., Weaver, D. K., & Sofie, S. (2012). Comparative toxicity of
 516 nanostructured alumina and a commercial inert dust for *Sitophilus oryzae* (L.) and
 517 *Rhyzopertha dominica* (F.) at varying ambient humidity levels. *Journal of stored*
 518 *products research*, 48, 81-90.

519 Stadler, T., López García, G., Gitto, J., & Buteler, M. (2017). Nanostructured alumina:
 520 biocidal properties and mechanism of action of a novel insecticide powder. *Bullettin of*
 521 *Insectology*, 70(1), 17-25.

522 Stejskal, V. (2015). Pest prevention during storage, transportation and handling of stored
 523 products. *Integrated Protection of Stored Products*, 111, 171-176.

524 Stejskal, V., Aulicky, R., & Kucerova, Z. (2014). Pest control strategies and damage potential
 525 of seed-infesting pests in the Czech stores-a review. *Plant Protection Science*, 50(4), 165-
 526 173.

527 Stejskal, V., Aulický, R., Kučerová, Z., & Lukáš, J. (2008). Method of sampling and
 528 laboratory extraction affects interpretation of grain infestation by storage pests. *Journal*
 529 *of Plant Diseases and Protection*, 115(3), 129-133.

530 Stejskal, V., Hubert, J., Aulicky, R., & Kucerova, Z. (2015). Overview of present and past
 531 and pest-associated risks in stored food and feed products: European perspective. *Journal*
 532 *of Stored Products Research*, 64, 122-132.

533 Stejskal, V., Hubert, J., Kucerova, Z., Munzbergova, Z., Lukas, J., & Zd Arkova, E. (2003).
 534 The influence of the type of storage on pest infestation of stored grain in the Czech
 535 Republic. *Plant Soil and Environment*, 49(2), 55-62.

536 Stejskal, V., Kosina, P., & Kanyomeka, L. (2006). Arthropod pests and their natural enemies
537 in stored crops in northern Namibia. *Journal of Pest Science*, 79(1), 51.

538 Tapondjou, A. L., Adler, C. F. D. A., Fontem, D. A., Bouda, H., & Reichmuth, C. H. (2005).
539 Bioactivities of cymol and essential oils of *Cupressus sempervirens* and *Eucalyptus*
540 *saligna* against *Sitophilus zeamais* Motschulsky and *Tribolium confusum* du Val. *Journal*
541 *of Stored Products Research*, 41(1), 91-102.

542 Tomé, H. V. V., Martins, G. F., Lima, M. A. P., Campos, L. A. O., & Guedes, R. N. C.
543 (2012). Imidacloprid-induced impairment of mushroom bodies and behavior of the native
544 stingless bee *Melipona quadrifasciata* anthidioides. *PLoS One*, 7(6).

545 Tomé, H. V. V., Barbosa, W. F., Martins, G. F., & Guedes, R. N. C. (2015). Spinosad in the
546 native stingless bee *Melipona quadrifasciata*: regrettable non-target toxicity of a
547 bioinsecticide. *Chemosphere*, 124, 103-109.

548 Van der Sluijs, J. P., Amaral-Rogers, V., Belzunces, L. P., Van Lexmond, M. B., Bonmatin, J.
549 M., Chagnon, M., Downs, C.A., Furlan, L., Gibbons, D.W., Giorio, C., Girolami, V.,
550 Goulson, D., Kreutzweiser, D.P., Krupke, C., Liess, M., Long, E., McField, M., Mineau,
551 P., Mitchell, E.A., Morrissey, C.A., Noome, D.A., Pisa, L., Settele, J., Simon-Delso, N.,
552 Stark, J.D., Tapparo, A., Van Dyck, H., van Praagh, J., Whitehorn, P.R., & Girolami, V.
553 (2015). Conclusions of the Worldwide Integrated Assessment on the risks of
554 neonicotinoids and fipronil to biodiversity and ecosystem functioning. *Environmental*
555 *Science and Pollution Research*, 22, 148–154.

556 Van Dijk, T. C., Van Staalduinen, M. A., & Van der Sluijs, J. P. (2013). Macro-invertebrate
557 decline in surface water polluted with imidacloprid. *PloS one*, 8(5).

558 Wang, X., Anadón, A., Wu, Q., Qiao, F., Ares, I., Martínez-Larrañaga, M. R., Yuan, Z., &
559 Martínez, M. A. (2018). Mechanism of neonicotinoid toxicity: impact on oxidative stress
560 and metabolism. *Annual review of Pharmacology and Toxicology*, 58, 471-507.

- Yasur, J., & Rani, P. U. (2013). Environmental effects of nanosilver: impact on castor seed germination, seedling growth, and plant physiology. *Environmental Science and Pollution Research*, 20(12), 8636-8648.
- Yasur, J., & Rani, P. U. (2015). Lepidopteran insect susceptibility to silver nanoparticles and measurement of changes in their growth, development and physiology. *Chemosphere*, 124, 92-102.

Tables

Table 1. X-ray diffraction (XRD) analysis of the nanostructured alumina.

Peak position ^a	B structure ^a	Crystallite size ^b
25.58	0.167	48.7
35.15	0.143	58.4
37.80	0.123	35.1
43.34	0.143	59.9
52.54	0.143	62.0
57.48	0.163	55.5
61.29	0.122	36.4
66.50	0.143	66.5
68.19	0.122	78.4
77.22	0.061	68.1

^a, °2θ Th; ^b, values are expressed in nm

Table 2. Adjusted estimated marginal (EM) means of the mortality of *Tribolium confusum*, *Oryzaephilus surinamensis*, and *Stegobium paniceum* exposed to nanostructured alumina (NSA).

Species	Mean $\pm$ SE	95% Confidence Interval	
		Lower bound	Upper bound
<i>T. confusum</i>	28.556 $\pm$ 1.628 b	25.296	31.816
<i>O. surinamensis</i>	23.037 $\pm$ 1.628 b	19.777	26.297
<i>S. paniceum</i>	36.083 $\pm$ 2.016 a	32.046	40.121

Data are expressed as mean mortality percentage $\pm$ standard error. Covariate (NSA dose) was evaluated at NSA = 151.23 mg kg⁻¹. Different letters indicate significant difference by pairwise comparison adjusted by Bonferroni correction for multiple comparisons.

612
613
614
615
616
617
618
619
620
621
622
623
624
625
626

Table 3. Median lethal concentration (LC₅₀) of nanostructured alumina (NSA) effective against adults of *Oryzaephilus surinamensis*, *Stegobium paniceum*, and *Tribolium confusum*.

Species	LC ₅₀ ^a	Intercept	<i>P</i>
<i>O. surinamensis</i>	0.44(0.23-1.02)	1.186	< 0.001
<i>S. paniceum</i>	1.10(0.60-10.70)	-0.138	0.544
<i>T. confusum</i>	127.17(60.24-305.92)	-0.978	0.001

^a, Concentration of the NSA that kills 50% of the exposed insects. Data are expressed as mg Kg⁻¹; in bracket, confidence interval. Pearson goodness of fit test: $\chi^2 = 3.379$; df = 11; $P = 0.985$.

628
629
630
631
632
633
634
635
636
637
638
639
640
641
642
643

Table 4. Effects of nanostructured alumina (NSA) on seeds germination, and radicle and shoot elongation of *Phaseolus vulgaris* seedlings.

	Control	NSA
Seed Germination ^a	7.60 ± 0.60	6.00 ± 0.95
Ipcotyle ^b	30.12 ± 7.71	18.00 ± 7.06
Root ^b	5.20 ± 0.78 a	10.68 ± 5.04 b

^a, % of germinated seeds; b, cm; Control, seeds not treated with NSA. Data are expressed as means $\pm$ standard error.

644

Table 5. Effects of nanostructured alumina (NSA) on plant of *Phaseolus vulgaris* grown in pot culture.

	<i>Control</i>	<i>NSA</i>
First internod ^a	2.59 ± 2.13	2.13 ± 0.39
Second internod ^a	5.76 ± 0.79	5.75 ± 0.66
Third internod ^a	6.70 ± 1.00	7.37 ± 0.50
Fourth internod ^a	0.67 ± 0.66 a	6.93 ± 1.25 b
Shoot (total)^a	15.07±1.20 a	22.76 ± 2.25 b
Leaves area ^b	56.93 ± 3.15	64.13 ± 1.72
Stoma density ^c	15.58 ± 0.36	13.25 ± 0.88
Root^a	12.61 ± 1.91	14.08 ± 1.28

^a, cm; ^b, cm²; ^c, No. stoma cm⁻². Data are expressed as means ± standard error. Different letters indicate significant difference between treatments (t-test, *P* < 0.05).

645

646

647

648

649

650

651

652

653

654

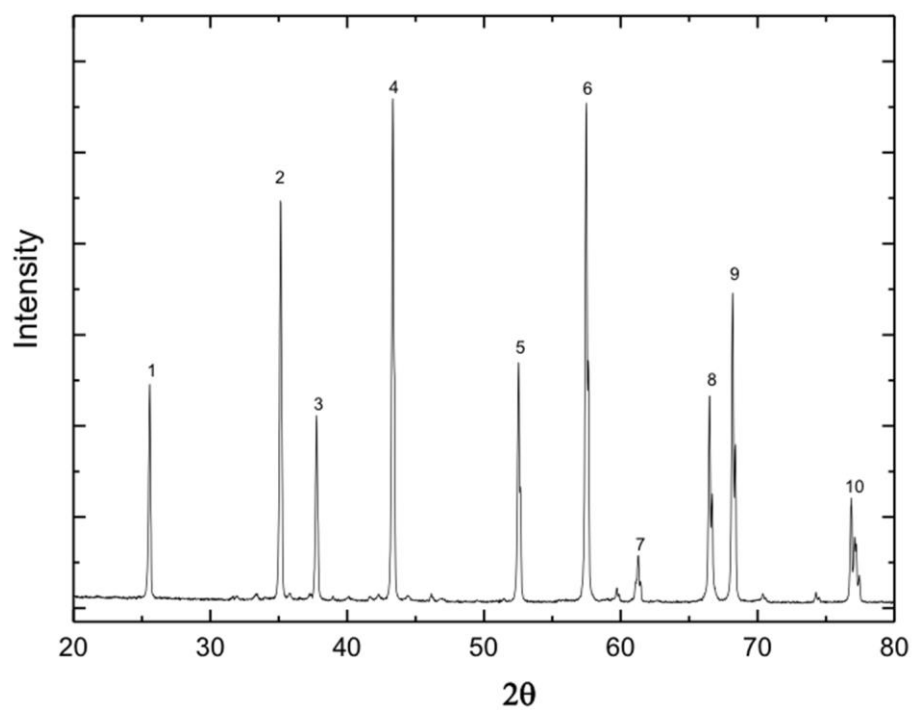


Figure 1. X-ray diffraction (XRD) spectra of the nanostructured alumina (NSA) particles

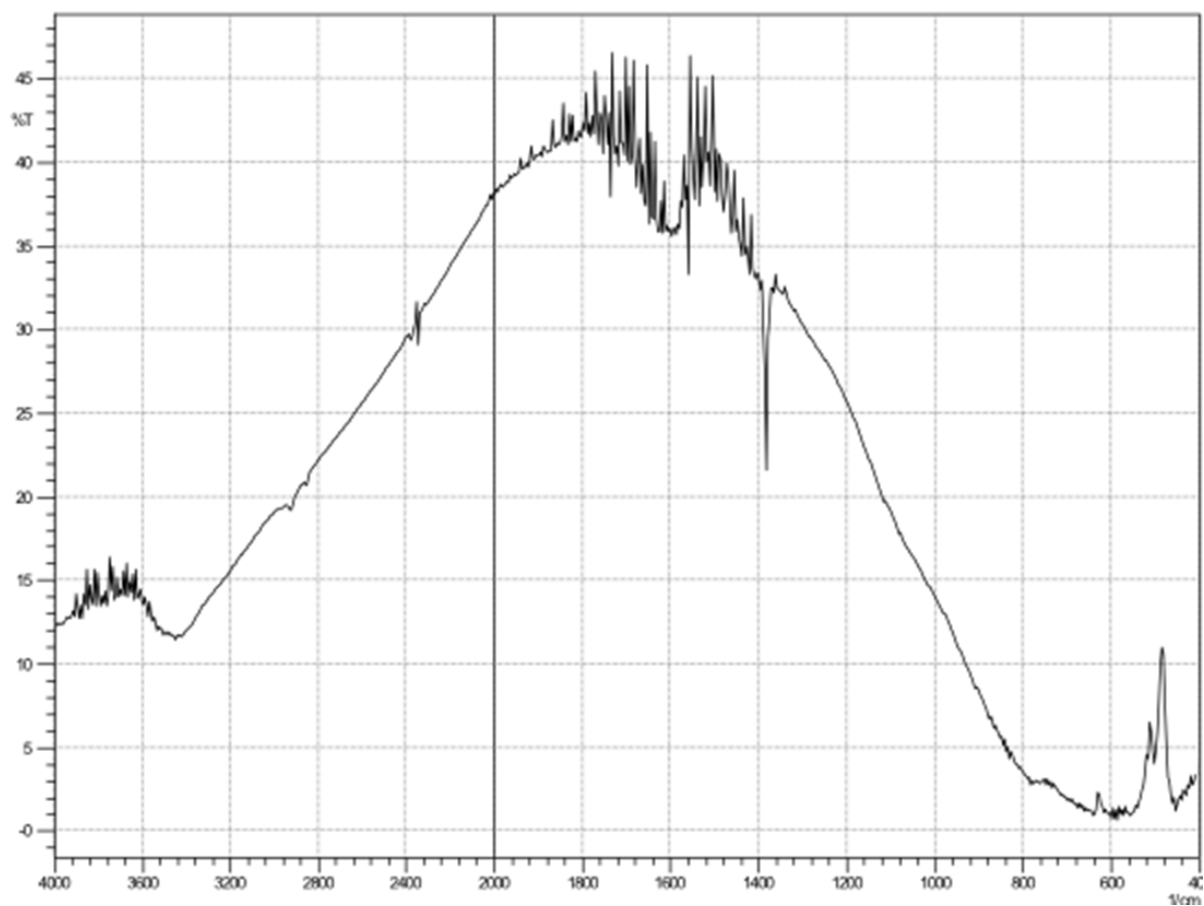


Figure 2. Fourier Transform Infrared Spectroscopy (FT-IR spectroscopy) spectra of nanostructured alumina (NSA) particles.

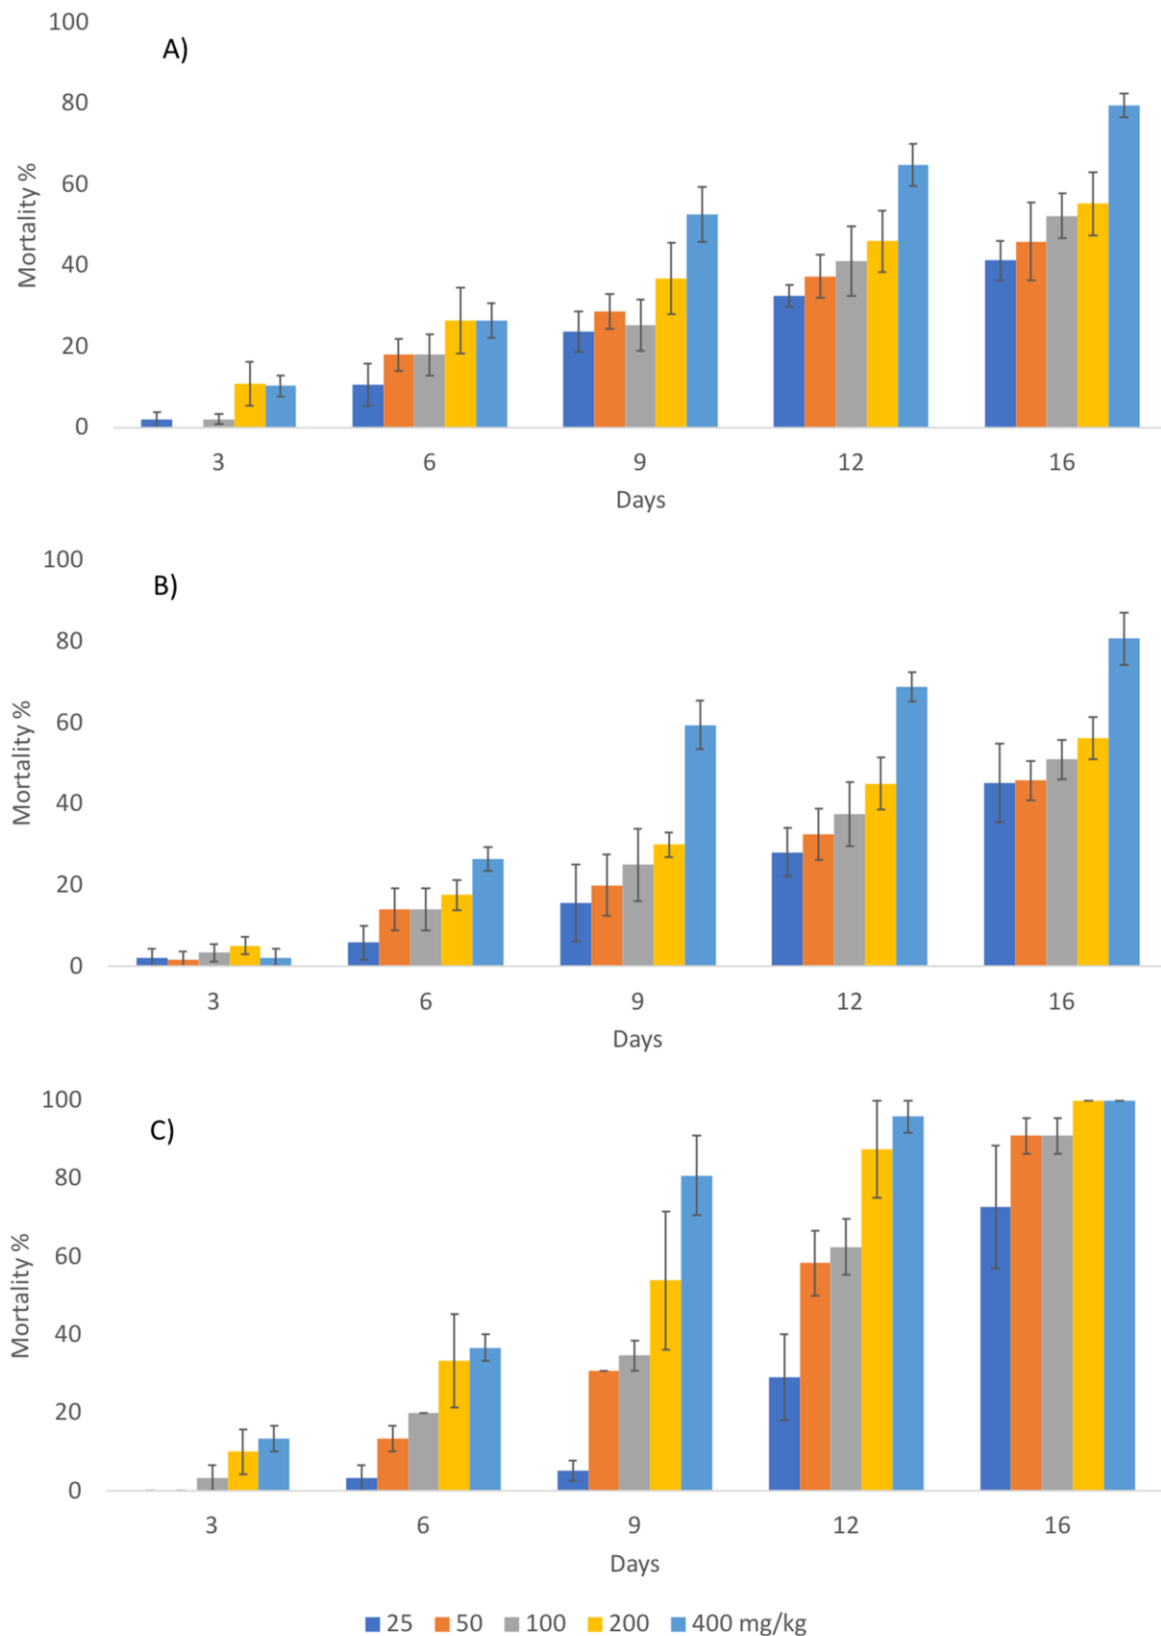


Figure 3. Mortality (%) (mean $\pm$ SE) of *T. confusum* (a) and *O. surinamensis* (b) *S. paniceum* (c) adults fed on beans treated with nanostructured alumina (NSA) particles.